

Magnetic susceptibility and heat capacity investigations of the unconventional spin-chain compound $\text{Sr}_3\text{CuPtO}_6$

S. Majumdar, V. Hardy,* M. R. Lees, and D. McK. Paul

Department of Physics, University of Warwick, Coventry CV4 7AL, United Kingdom

H. Rousselière and D. Grebille

Laboratoire CRISMAT, UMR 6508, Boulevard du Maréchal Juin, 14050 Caen cedex, France

The Heisenberg spin chain compound $\text{Sr}_3\text{CuPtO}_6$ is investigated by magnetic susceptibility and heat capacity measurements. $\text{Sr}_3\text{CuPtO}_6$ has an unconventional chain structure in the sense that i) the spin half copper atoms are arranged in a zigzag chain structure, and ii) neighboring Cu atoms along the chains are separated by spin zero platinum atoms. We report that this compound shows broad features in the temperature dependence of both the magnetic contribution to the heat capacity and the magnetic susceptibility. Despite the unconventional nature of the spin chain structure, this set of data exhibits good agreement with theoretical models for a classical $S = \frac{1}{2}$ Heisenberg spin chain compound. The values of the intra-chain coupling constant, obtained by different techniques, are found to be very close to each other. The low temperature heat capacity data (below ~ 6 K) exhibit a deviation from the theoretically expected behavior, which could be related to a small energy gap in the spin excitation spectrum.

PACS numbers: 75.40.Cx, 75.50.Ee, 75.10.Pq

I. INTRODUCTION

A new class of one-dimensional (1D) magnetic compounds with the general formula A_3XYO_6 ($\text{A} = \text{Sr}, \text{Ca}$; $\text{X}, \text{Y} = \text{transition metals}$) has attracted particular interest recently.¹ These materials crystallize in a K_4CdCl_6 -type rhombohedral structure, which consists of infinite chains built up of alternating face-sharing YO_6 octahedra and XO_6 trigonal prisms. These YO_6 - XO_6 chains are separated from each other by A^{2+} cations and constitute a hexagonal cross-sectional arrangement perpendicular to the chain direction. Depending upon the nature and the oxidation states of the cations at the X and the Y sites, these materials present a range of low dimensional magnetic phenomena.² In this class of materials, $\text{Sr}_3\text{CuPtO}_6$ is reported to be a spin half Heisenberg antiferromagnet (AFM) chain compound.^{2,3,4}

From a crystallographic point of view, $\text{Sr}_3\text{CuPtO}_6$ does not constitute an ideal linear spin chain structure⁵. Firstly, due to the presence of Cu^{2+} cations at the X site, the K_4CdCl_6 -type rhombohedral structure undergoes a monoclinic distortion. The Pt^{4+} ions stay at the center of the PtO_6 octahedra maintaining a linear structure, whereas the Cu^{2+} ions move from the center of the CuO_6 trigonal prisms to their faces. Successive Cu^{2+} ions on a chain are displaced away from the chain axis in opposite directions, resulting in a zigzag chain structure with a Cu-Cu bond angle of 160.94° (see Fig. 1). Secondly, along each chain, neighboring $S = \frac{1}{2}$ Cu^{2+} ions are separated by a Pt^{4+} ion. In the presence of a strong octahedral crystal field, the Pt^{4+} ions adopt a low spin

ground state with zero effective spin. This results in a $\frac{1}{2}-0-\frac{1}{2}-0-\frac{1}{2}-\dots$ type of spin chain structure in which the $S = \frac{1}{2}$ inter-spin separations parallel and perpendicular to the chains are almost equal. Prompted by this fact, Claridge *et al.*³ analyzed the magnetic susceptibility data of $\text{Sr}_3\text{CuPtO}_6$ considering both intra-chain (J) and inter-chain (J') couplings among the Cu^{2+} ions. From their analysis, using a modified Bonner and Fisher model⁶, they reported that $J = 24.7$ K and $J' = 7.3$ K. Since $J/J' \sim 3$, they concluded that the compound should not be considered as a 1D magnetic system. However, the broad maximum observed in the magnetic susceptibility data^{2,3} gives a strong indication that the compound does indeed have the characteristics of a low-dimensional magnetic system. As a result, the magnetic status of $\text{Sr}_3\text{CuPtO}_6$ remains unclear.

In this paper, we present the results of a thorough investigation of the magnetic susceptibility and heat capacity behavior of single crystal samples of $\text{Sr}_3\text{CuPtO}_6$. While there have been studies of the magnetic susceptibility of this compound^{2,3,7}, the present paper reports the first investigation of the heat capacity of this material. Despite the fact that heat capacity can provide important information about the magnetic character of spin chain systems, very little heat capacity data have been published to date for the A_3XYO_6 class of compounds^{8,9,10,11}.

The theoretical model of Bonner and Fisher has been successfully used in the past to fit the experimental susceptibility data for $S = \frac{1}{2}$ spin chain systems¹². This model is based on the extrapolation of numerical calculations for a finite number of spins (≤ 11) and is valid in a limited temperature range ($T \geq \frac{1}{2}J$, where J is the intra-chain coupling constant in kelvin). Recently Klümper, Johnston, and co-workers^{13,14} have used the Bethe ansatz approach to formulate a model for the

*Permanent address: Laboratoire CRISMAT, UMR 6508, Boulevard du Maréchal Juin, 14050 Caen cedex, France.

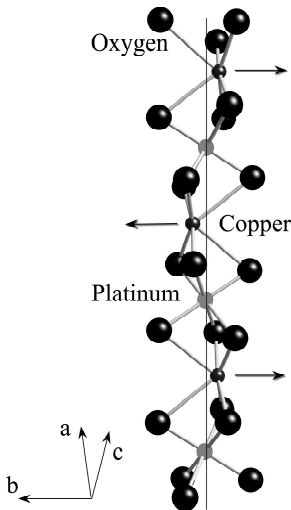


FIG. 1: A single $\text{CuO}_6\text{-PtO}_6$ chain in the crystal structure of $\text{Sr}_3\text{CuPtO}_6$. The line through the platinum atoms indicates the direction of the chain axis. The arrows indicate the displacement of the copper atoms from the chain axis resulting in the formation of a zigzag chain structure. Each chain is separated from the others by the Sr^{2+} ions.

$S = \frac{1}{2}$ Heisenberg spin chain system, which should be valid over the entire temperature range. This model is an extension of previous theoretical work^{15,16}. In the present paper, the majority of the fitting has been carried out using this new analytical model proposed by Johnston and co-workers (hereafter called the Johnston model)¹³. The Bonner-Fisher model has also been used for comparison. Throughout the paper, we have adopted the convention where the spin Hamiltonian, $\mathcal{H}$, is defined as $\mathcal{H} = 2Jk_B \sum_i \mathbf{S}_i \cdot \mathbf{S}_{i+1}$, where $\mathbf{S}_i$ is the i -th spin on the chain and k_B is the Boltzmann constant.

II. EXPERIMENTAL DETAILS

The needle shaped crystals of $\text{Sr}_3\text{CuPtO}_6$ used in this investigation were prepared by a K_2CO_3 flux method as described in reference³. The crystals were analyzed by x-ray diffraction using $\text{Mo } K_\alpha$ radiation on a Bruker Nonius Kappa CCD single crystal x-ray diffractometer. The cell refinement showed that the crystals have a monoclinic structure (space group C2/c) with lattice parameters $a = 9.34(1) \text{ \AA}$, $b = 9.64(1) \text{ \AA}$, $c = 6.68(1) \text{ \AA}$ and $\beta = 91.91(5)^\circ$, which are in good agreement with the literature⁵. The rod axis of the crystals was found to be along the $[201]$ direction, which coincides with the $\text{CuO}_6\text{-PtO}_6$ chain direction. The magnetic susceptibility measurements were carried out using a Quantum Design SQUID magnetometer in the temperature (T) range 2-400 K with the applied magnetic field (H) parallel to the chain direction. The zero field heat capacity (C) measurements were

performed by a relaxation method using a Quantum Design Physical Properties Measurement System (PPMS). The C versus T data in the temperature range 1.9 to 300 K were recorded with a conventional ^4He insert, whereas, the data collected below 1.9 K were recorded using a ^3He refrigerator option. Since the mass of each crystal is typically $\sim 1\text{-}2 \text{ mg}$, an assembly of 6 crystals, with their rod axis aligned, were used for both the magnetization (M) and the heat capacity measurements.

In order to obtain information about the short range magnetic correlations from the heat capacity data, it is necessary to estimate the lattice contribution to the heat capacity (C_{lat}). It is therefore, important to measure a non-magnetic reference compound with the same crystal structure and containing elements with similar masses. For this purpose, a ceramic sample of the isostructural compound $\text{Sr}_3\text{ZnPtO}_6$ was prepared by the usual solid state reaction technique¹⁷. This compound was found to be essentially nonmagnetic. The small Curie constant $c_{cw} \sim 2.6 \times 10^{-3} \text{ emu/K-mol}$, derived from the magnetic susceptibility versus temperature data for $\text{Sr}_3\text{ZnPtO}_6$, corresponds to only 0.1% of the Pt^{4+} ions on the prismatic sites being in the high-spin ($S = 2$) magnetic state.

III. RESULTS

A. Susceptibility

Figure 2 shows the magnetic susceptibility ($\chi = M/H$) versus temperature data of $\text{Sr}_3\text{CuPtO}_6$ in the temperature range 2-400 K with the applied magnetic field (10 kOe) along the $[201]$ direction. The low temperature $\chi(T)$ data show a rise with decreasing temperature below 10 K, similar to that observed in a previous investigation³ on this compound. Such a feature has also been observed in a number of other spin chain compounds^{18,19} and it is generally thought to arise from the presence of broken chains and/or paramagnetic impurities; both effects lead to a Curie like term.²⁰ At intermediate temperatures, the susceptibility versus temperature data shows a broad peak around 32 K, which is typical of short range magnetic order in a spin chain system. The high temperature data (250-400 K) shows Curie-Weiss behavior along with a temperature independent positive term χ_0 .

For a quantitative analysis of the susceptibility versus temperature data, we express χ as a sum of three terms as in reference²¹ with

$$\chi = \chi_{\text{add}} + \chi_0 + \chi_{\text{chain}} \quad (1)$$

The term $\chi_{\text{add}} = c_{\text{add}}/(T - \theta_{\text{add}})$ is a Curie-like term coming from broken chains or paramagnetic impurities in the system. The term χ_0 is a combination of the van Vleck paramagnetic term and the diamagnetic contributions from the atomic cores. χ_{chain} is the contribution coming from the 1D magnetic correlations among the spins. This can be approximated using the Johnston model (equation (50) of reference¹³) for the $S = \frac{1}{2}$

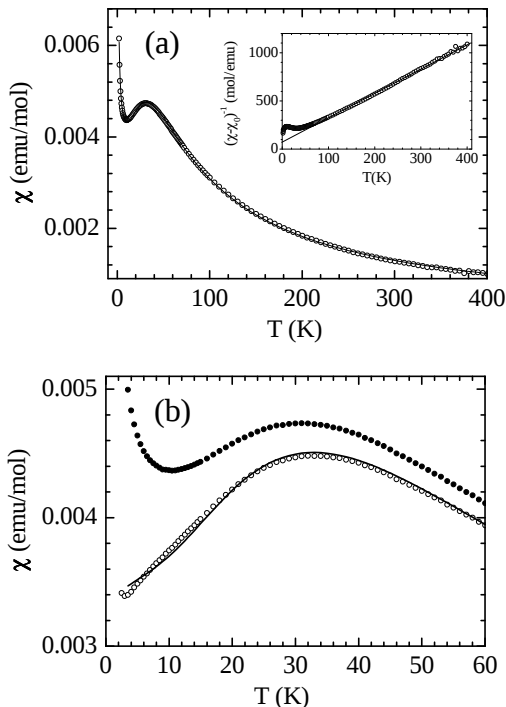


FIG. 2: The upper panel (a) shows the magnetic susceptibility versus temperature data in the temperature range 2 - 400 K with the applied field ($H = 10$ kOe) parallel to the [201] direction. The solid line through the data points is a global fit of the data using a Johnston term, a temperature independent term, and a Curie term (as discussed in the text). The inset in the upper panel shows the inverse susceptibility versus temperature data with the temperature independent term (χ_0) removed. The solid line in the inset shows a linear fit of the data in the temperature range 250 - 400 K. The lower panel (b) shows the low temperature (2-60 K) behavior of the susceptibility with $H = 10$ kOe, applied parallel to the [201] direction. The data points with filled circles show the total susceptibility data, whereas the data points with open circles indicate susceptibility after the Curie contribution (χ_{add}) and the temperature independent positive term (χ_0) have been subtracted. The solid line through the open circles shows a Johnston model fit associated to the spin chain contribution (χ_{chain}).

uniform linear chain system where we write $\chi_{chain}(T) = \chi\{J, g\}(T)$ where J and g (Landé g factor) are the free parameters. With these considerations, we have fitted our $\chi(T)$ data to equation 1 in the temperature range 2-400 K (solid line in Figure 2). The good quality of the fit over the full temperature range indicates that the Johnston model can be used to describe the susceptibility behavior of $\text{Sr}_3\text{CuPtO}_6$. The parameters obtained from the fitting are: $J = 25.7(1)$ K, $g = 2.050(3)$, $\chi_0 = 8.1(7) \times 10^{-5}$ emu/mol, $c_{add} = 0.0055(1)$ emu-K/mol and $\theta_{add} = -0.14(5)$ K. Similar fitting for $T > 13$ K ($\sim \frac{1}{2}J$), using the Bonner-Fisher model for χ_{spin} , produces a value of $J = 25.3(1)$ K, which compares well

with the result obtained using the Johnston model. The value of J is also in good agreement with the value (26.1 K) estimated by Nguyen *et al.*⁴ using the Bonner-Fisher model.

The Curie constant associated with χ_{add} corresponds to a moment of $1.73 \mu_B$ residing on $\sim 1.5\%$ of the Cu atoms present in the sample. The value of χ_{add} remains practically unchanged if one sets $\theta_{add} = 0$. This concentration of free Cu^{2+} ions is comparable with the values previously reported in some other Cu^{2+} based spin chain compounds^{18,19}.

At high temperatures (250-400 K), the $1/(\chi(T) - \chi_0)$ versus T plot (see inset of the upper panel) is found to be linear with the value of χ_0 obtained from the global fitting (2-400 K) of our data to equation 1. This is expected, because at high temperatures, χ_{add} becomes negligible and χ_{spin} reduces to a Curie-Weiss term. Additional confidence in the reliability of this χ_0 value comes from fitting the high temperature $\chi(T) - \chi_0$ data to a simple Curie-Weiss expression, where one finds an effective moment $p_{eff} = 1.77(2) \mu_B/\text{Cu}^{2+}$, which is close to the theoretical value ($1.73 \mu_B$), and a paramagnetic Curie temperature $\theta_p = -26 (\pm 2)$ K that compares well with the J value as expected for an $S = \frac{1}{2}$ spin chain system.

The lower panel of figure 2 is an expanded view of the susceptibility data below 60 K, showing the total $\chi(T)$ (filled circles), the χ_{chain} data (open circles) and a fit using the Johnston formula (solid line). It should be noted that even on this expanded scale, the overall agreement of the χ_{chain} data to the Johnston fitting is found to be good. However, below ~ 20 K a discrepancy between the experimental data and the fitted line appears. In fact, the change in the slope expected in the Johnston model around $T \sim 0.4J$ K (about 10 K in the present case), is not present in our data. Given the fact that $\text{Sr}_3\text{CuPtO}_6$ has an unconventional chain structure, some departures in the magnetic behavior from the theoretical model are not unexpected. Nevertheless, it must also be borne in mind that in the temperature range considered here, the χ_{chain} data is very sensitive to the subtraction of χ_{add} , which may introduce some uncertainty in the resulting χ_{chain} values.

In order to better understand the low temperature behavior of $\text{Sr}_3\text{CuPtO}_6$, it is useful to investigate the temperature dependence of the heat capacity of this system, which is expected to be much less affected by additional contributions from broken chains or paramagnetic impurities.

B. Heat capacity

The total heat capacity of $\text{Sr}_3\text{CuPtO}_6$ as a function of temperature (1.9-300 K) is shown in figure 3a (inset). This data contains no signature of long range magnetic ordering in this temperature range. Figure 3 also depicts the $C(T)$ of the nonmagnetic isostructural compounds $\text{Sr}_3\text{ZnPtO}_6$. At low temperatures (be-

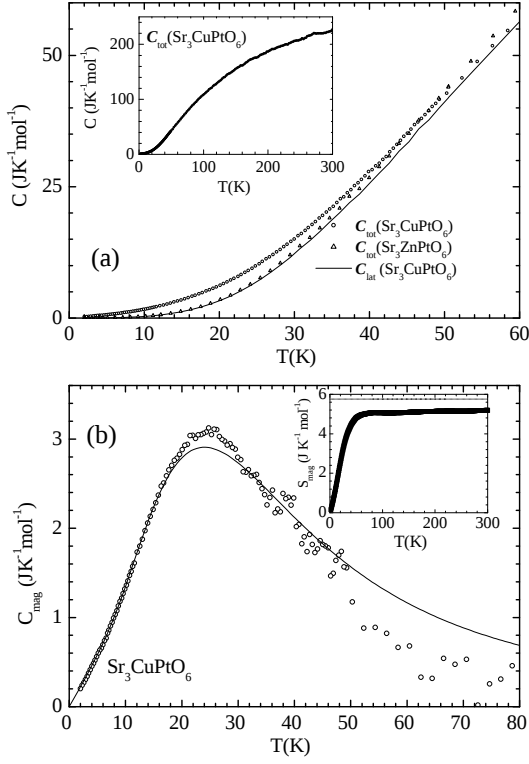


FIG. 3: The upper panel (a) shows the heat capacity versus temperature data of $\text{Sr}_3\text{CuPtO}_6$ in the temperature range 1.9 - 60 K. The heat capacity data of the nonmagnetic isostructural compound $\text{Sr}_3\text{ZnPtO}_6$ is also shown in the figure along with the lattice contribution of the heat capacity of $\text{Sr}_3\text{CuPtO}_6$ as calculated (see text for details) from the heat capacity data of $\text{Sr}_3\text{ZnPtO}_6$. The inset in the upper panel shows a full view (1.9 - 300 K) of the heat capacity versus temperature data of $\text{Sr}_3\text{CuPtO}_6$. The lower panel (b) shows the magnetic contribution to the heat capacity (C_{mag}) of $\text{Sr}_3\text{CuPtO}_6$ as a function of temperature along with the curve predicted by the Johnston model (solid line) for $J = 25.5$ K. The inset shows the magnetic entropy versus temperature data for $\text{Sr}_3\text{CuPtO}_6$, and the dotted line in the inset denotes the theoretical value of the entropy ($R \ln 2$) for an $S = \frac{1}{2}$ system.

low about 50 K), $C_{\text{tot}}(\text{Sr}_3\text{CuPtO}_6)$ is larger in value than $C_{\text{tot}}(\text{Sr}_3\text{ZnPtO}_6)$. This is clearly due to an additional contribution to the heat capacity of magnetic origin for the Cu compound. It is expected that the magnetic contribution to $C_{\text{tot}}(\text{Sr}_3\text{CuPtO}_6)$ should tend to zero at high temperatures. There is a difference between $C_{\text{tot}}(\text{Sr}_3\text{ZnPtO}_6)$ and $C_{\text{tot}}(\text{Sr}_3\text{CuPtO}_6)$ even at 300 K, which is due to the mass difference of the Cu and the Zn atoms. In order to calculate the lattice contribution, C_{lat} , of $\text{Sr}_3\text{CuPtO}_6$ from the heat capacity data of $\text{Sr}_3\text{ZnPtO}_6$, a careful mass correction to the data is required. In the present case we have used a phenomenological scaling of the Debye temperature (Θ_D) with two scaling factors (see appendix) to obtain the C_{lat} from the heat capacity of the non-magnetic reference sample. It

should be noted that the scaling for C_{lat} has only a weak effect at low temperatures. $C_{\text{lat}}(\text{Sr}_3\text{CuPtO}_6)$ is almost superimposed onto $C_{\text{tot}}(\text{Sr}_3\text{ZnPtO}_6)$ below about 40 K. Since this is the region of interest for the analysis of the 1D magnetic features, these should not be significantly affected by any imperfection in the model used to derive $C_{\text{lat}}(\text{Sr}_3\text{CuPtO}_6)$.

The lower panel of figure 3 shows the magnetic contribution to the heat capacity of $\text{Sr}_3\text{CuPtO}_6$, $C_{\text{mag}}(T)$, that was obtained by subtracting the lattice contribution $C_{\text{lat}}(T)$ from the total heat capacity $C_{\text{tot}}(T)$. The main feature is a broad peak at low temperature, as expected in a 1D magnetic system¹². In their theoretical investigation of $S = \frac{1}{2}$ Heisenberg antiferromagnetic chains, Johnston *et al.*¹³ have proposed analytical expressions for the temperature dependence of the heat capacity. The solid line in figure 3 is the curve predicted by this model (equations 54a-c of reference¹³) for $J = 25.5$ K. It is worth emphasizing that there are no free parameters other than J in this model. On the scale of Figure 3, only curves obtained using a narrow range (± 0.5 K) of J values around 25.5 K provide good overall agreement with the experimental data. The curve corresponding to $J = 25.5$ K gives the best fit for $T < \frac{1}{2}J$ and the quality of the agreement is quite satisfactory up to about 40 K. Above $T \sim 50$ K, the $C_{\text{mag}}(T)$ data clearly departs from the model, a behavior which can be ascribed to the uncertainty in the estimation of C_{lat} (for instance, at $T \sim 60$ K, the expected magnetic contribution is just 2% of the measured total heat capacity). In the Bonner-Fisher model, the intra-chain coupling is related to the temperature T_{max} corresponding to the maximum in $C_{\text{mag}}(T)$ data as $T_{\text{max}} \simeq 0.962J$. Considering T_{max} in the range 24-25.5 K, one obtains J value lying between 25 K and 26.5 K, which is in good agreement with the value of J given by the Johnston model above.

The inset in the lower panel of figure 3 displays the temperature dependence of the magnetic entropy derived by $S_{\text{mag}}(T) = \int_0^T \left(\frac{C_{\text{mag}}(T')}{T'} \right) dT'$.²² One observes that the calculated entropy saturates slightly below the theoretical value, $R \ln 2 = 5.76$ J/mol-K, expected for $S = 1/2$. This apparent *missing* entropy probably just reflects the uncertainty in the estimation of $C_{\text{lat}}(T)$.

In order to get a more comprehensive view of the 1D magnetic behavior of $\text{Sr}_3\text{CuPtO}_6$, we have extended our heat capacity measurement down to 0.35 K. Figure 4 shows the C_{mag}/T versus T data below 11 K, while the inset in figure 4 shows the temperature dependence of the C_{mag} data below 6 K. Around 1.5 K, C_{mag} contains a small feature (which is more clearly visible in the C_{mag}/T versus T plot), and then tends smoothly to zero as T is decreased further. This may be a signature of three dimensional (3D) long range magnetic ordering or of a spin-Peierls-like transition. However, the occurrence of such a transition appears to be in contrast with the work of Irons *et al.*⁷, who reported the absence of any anomaly in the a.c. susceptibility measurements down to 0.27 K on a polycrystalline sample of $\text{Sr}_3\text{CuPtO}_6$. In order to

understand the significance of this feature, further investigations based on neutron scattering measurements are required. For the present analysis, we decided to restrict ourselves to the temperature range $T \geq 2$ K, for which C_{mag} is presumably related to the short range intra-chain coupling only.

In case of an AFM spin chain system like $\text{Sr}_3\text{CuPtO}_6$, C_{mag} is expected to show a linear T dependence, $C_{mag} = \gamma_{mag}T$, at low temperatures (approximately, $T < J/5$ which is below 5 K in our case). Our $C_{mag}(T)$ data in figure 4 (inset) shows a quasi-linear behavior in the temperature range 2-6 K, but clearly extrapolates to a finite T intercept of about 0.5 K at $C_{mag} = 0$. Such a behavior suggests the possibility of a small gap of $\Delta \sim 0.5$ K in the spin excitation spectrum. Although, a spin gap should not exist in case of a uniform $S = \frac{1}{2}$ spin chain system, the possibility of a gap cannot be ruled out in the case of $\text{Sr}_3\text{CuPtO}_6$, with its unconventional spin chain structure.

In figure 4, we have shown C_{mag}/T behavior predicted by the Johnston model (down to $T = 1$ K) with $J = 25.5$ K along with the experimental data. While the Johnston model well represents the experimental data down to 5 K, a deviation is visible in the low temperature data. The experimental C_{mag}/T contains a clear downward curvature below 5 K, which is absent in the Johnston model that shows a rather constant $C_{mag}(T)/T$ behavior consistent with the expected linear T dependence of the C_{mag} data in this temperature range (1-5 K). This departure from the Johnston model behavior around 5 K cannot be simply attributed to the small feature observed around 1.5 K. If a spin gap is responsible for such a departure, to a first approximation, it can be accounted by a phenomenological relation $C_{mag}^\Delta/T = \gamma_{mag}^\Delta \exp(-\Delta/T)$ at low temperatures. The dotted line in figure 4 shows the fitting of C_{mag}^Δ/T to the data in the temperature range 2-5 K along with an extrapolation slightly below and above 2 K and 5 K respectively. The parameters estimated by the fitting are found to be $\gamma_{mag}^\Delta = 0.128 \text{ JK}^{-2}\text{mol}^{-1}$ and $\Delta = 0.64$ K. This phenomenological spin gap model can account for the downward curvature in the $C_{mag}(T)/T$ data below 5 K. According to the Johnston model, for a $S = \frac{1}{2}$ AFM spin chain, the coefficient of the linear term (γ_{mag}) in C_{mag} is related to the intra-chain coupling parameter as $\gamma_{mag} = R/3J$, where R is the universal gas constant. Although, strictly speaking, this relation is valid for an ideal gap-less spin chain system, we have used the relation in the present context to estimate the value of J . The value of J , obtained by inserting the value of γ_{mag}^Δ in the above relation, is found to be 22.2 ± 0.5 K, which is close to the values of J obtained from other methods.

IV. DISCUSSION

The present magnetic susceptibility and heat capacity investigations on single crystals of $\text{Sr}_3\text{CuPtO}_6$ show

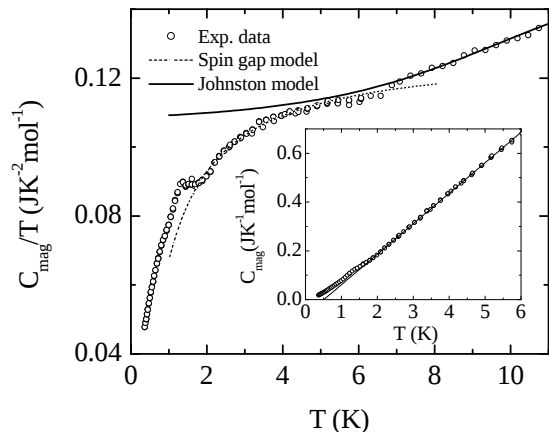


FIG. 4: The low temperature (down to 0.35 K) magnetic heat capacity versus temperature data of $\text{Sr}_3\text{CuPtO}_6$ along with the curve (solid line) predicted by Johnston model (down to 1 K) for $J = 25.5$ K. and the curve (dotted line) obtained by fitting $C_{mag}^\Delta = \gamma_{mag}^\Delta T \exp(-\Delta/T)$ to our data in the temperature range 2- 5 K and then extrapolated below and above 2 K and 5 K respectively. The inset shows the C_{mag} versus T data below 6 K. The line emphasizes the quasi-linear behavior of the data in the temperature range 2-6 K.

that there is a good overall agreement between our experimental data and the theoretical predictions for an $S = \frac{1}{2}$ Heisenberg AFM spin chain system. The values of the characteristic coupling parameter J , obtained from different measurements, are reasonably consistent.

Such good agreement with standard spin chain models is rather surprising for a compound whose one-dimensional magnetic character was recently questioned^{3,7}. The doubts raised were based upon the large value of the inter-chain coupling parameter (J'), derived from an analysis of the magnetic susceptibility, leading to a ratio $J/J' \sim 3$. Our susceptibility analysis discussed so far in the text has been performed without considering any inter-chain coupling parameter (i.e., $J' = 0$). In order to get an idea of the inter-chain coupling parameter, we have reanalyzed our susceptibility data with the relation proposed by Hatfield⁶ and previously used by Claridge *et al.*³. We found that this mean field approach can improve the quality of the fitting with the addition of an AFM inter-chain coupling parameter. The best fit is obtained for $J = 25.1 (\pm 0.1)$ K and $J' = 4.3 (\pm 0.2)$ K. The J' value is slightly less but still comparable with the value 7.3 K reported by Claridge *et al.*³. However, one should be careful in interpreting the value of J' from this kind of analysis. For low dimensional magnetic systems (with small and weakly T -dependent χ), the introduction of an additional fitting parameter, J' , can often lead to unphysical results. In the case of $\text{Sr}_3\text{CuPtO}_6$, such a large value of J' appears to be inconsistent with the global magnetic behavior, particularly the absence of long range magnetic order down to 2 K. A finite value of the inter-chain coupling should eventually lead to a three

dimensional ordering at a temperature T_N and theoretical models have established relationships between T_N and the coupling parameters (J and J') for the weakly coupled linear chain systems. For $S = \frac{1}{2}$ AFM Heisenberg chains, the model proposed by Oguchi²³, based on a Green's function method, has been used extensively²⁴. Recently, Schulz²⁵ has proposed another model relating T_N , J and J' for weakly coupled $S = \frac{1}{2}$ chains, which is based on a mean-field approximation for the inter-chain coupling and exact results for the resulting effective 1D problem. Both these models deal with a square lattice of the spin chains and as outlined by Lines *et al.*²⁶, corrections are required to apply these models to systems with a hexagonal arrangement of spin chains, as is the case for $\text{Sr}_3\text{CuPtO}_6$. With $J = 25.5$ K, and $T_N \leq 2$ K (since, there is no 3D order at least down to 2 K), both the Oguchi and the Schulz models predict an upper limit for the inter-chain coupling constant J' of 0.2 K. Therefore, it is clear that the large value of J' derived previously, by fitting the Hatfield model to the susceptibility data, may not be reliable. With $J' \leq 0.2$ K, one obtains the *lower boundary* of the ratio of the intra-chain and inter-chain coupling parameters to be approximately 130 ($J/J' \geq 130$) and this ratio is more consistent with the 1D magnetic character of $\text{Sr}_3\text{CuPtO}_6$.

Now the question is how to reconcile such a large J/J' ratio with the fact that the distance between two neighboring Cu^{2+} ions is approximately the same along and perpendicular to the chain. It is well known that the strength of the exchange coupling not only depends upon the distance, but also on the nature of the exchange pathway. From the viewpoint of the mediation of the exchange interaction between Cu^{2+} ions, the situation is very different parallel and perpendicular to the chains. Although the Pt^{4+} ions located in between the Cu^{2+} ions along the chains are in the low spin state ($S = 0$), they possess unfilled 3d orbitals and can thus participate in the exchange interaction. A similar mechanism cannot be expected for the Sr^{2+} ions located in between the CuO_6 - PtO_6 chains. Such a difference in the exchange pathway can qualitatively explain the large J/J' ratio in $\text{Sr}_3\text{CuPtO}_6$.

Finally, let us consider the low temperature (0.35-6 K) heat capacity data for $\text{Sr}_3\text{CuPtO}_6$, which revealed some deviation from the $S = \frac{1}{2}$ 1D AFM Heisenberg model. Although, they are also visible in χ_{chain} data (figure 3), such deviations can be studied more precisely in C_{mag} data. The latter data led us to propose the existence of a small energy gap in the spin excitation spectra. A uniform half-odd integral spin chain system is supposed to be gapless²⁷. One simple explanation for the origin of a small gap is a weak modulation in the strength of the exchange interaction along the chain²⁸. The zigzag nature of the spin chain in $\text{Sr}_3\text{CuPtO}_6$ may result in such a modulation.²⁹

In conclusion, we have performed a detailed investigation of the magnetic susceptibility and the heat capacity behavior of the compound $\text{Sr}_3\text{CuPtO}_6$. The use of a

nonmagnetic iso-structural compound ($\text{Sr}_3\text{ZnPtO}_6$) has enabled us to extract the magnetic contribution to the heat capacity. Both the magnetic susceptibility and the heat capacity were found to be consistent with the Johnston and Bonner-Fisher models for an $S = \frac{1}{2}$ AFM spin chain, with similar values of the intra-chain coupling parameters ($J \sim 25.5$ K). Based on the fact that there is no long range magnetic order observed in this system, at least down to 2 K, the *lower limit* of the ratio of the intra-chain and inter-chain coupling parameters is expected to be ~ 130 . These observations, in contrast to the previous reports^{3,7}, clearly identify $\text{Sr}_3\text{CuPtO}_6$ as a $S = \frac{1}{2}$ spin chain compound with 1D magnetic character. Deviations from the 1D uniform $S = \frac{1}{2}$ Heisenberg models were observed in the low temperature regime, which indicate the possible existence of a gap in the spin excitation spectrum.

We acknowledge the financial support of the EPSRC (UK) for this project.

APPENDIX: CALCULATION OF C_{lat}

According to the Debye model of lattice heat capacity,

$$C_{\text{lat}}(T) = 3pRD[\theta_D(T)/T] \quad (\text{A.1})$$

where p is the number of atoms per molecule, R is the gas constant, $\theta_D(T)$ is the Debye temperature, and $D(x) = (3/x^3) \int_0^x [z^4 e^z / (1 - e^z)^2] dz$ is the Debye function. The problem of finding C_{lat} for a magnetic sample reduces to the problem of deriving the Debye temperature of the magnetic sample, $\theta_D^{\text{sam}}(T)$ from that of a non-magnetic isostructural reference compound, $\theta_D^{\text{ref}}(T)$, which can be directly derived from the total heat capacity $C_{\text{tot}}(T)$ of the reference sample by inverting equation A.1. A one parameter scaling of the Debye temperature ($\theta_D^{\text{sam}}(T) = r\theta_D^{\text{ref}}(T)$) (where r is a constant) is found to be inadequate as there is no r value leading to a $C_{\text{lat}}(\text{Sr}_3\text{CuPtO}_6)$ which tends to $C_{\text{tot}}(\text{Sr}_3\text{CuPtO}_6)$ at 300 K, while lying below it for $T < 300$ K. The former requirement is based on the fact that at 300 K, the theoretical magnetic contribution to the heat capacity for $S = \frac{1}{2}$ Heisenberg chain with $J \sim 25$ K, is expected to be only 0.02% of the total heat capacity of $\text{Sr}_3\text{CuPtO}_6$. The failure of this one parameter scaling led us to use an extension of this approach with two phenomenological factors, corresponding to the highest (T_H) and lowest (T_L) temperatures of our data. We can express $\theta_D^{\text{ref}}(T) = \theta_D^{\text{ref}}(T_L) + [\theta_D^{\text{ref}}(T_H) - \theta_D^{\text{ref}}(T_L)] f(T)$, where $f(T)$ is a function such as $f(T_L) = 0$ and $f(T_H) = 1$. Owing to the structural equivalence of the magnetic and the non-magnetic reference compounds, we assumed that $\theta_D^{\text{sam}}(T)$ can be approximated by a similar expression, keeping the same function $f(T)$. The θ_D^{sam} values at T_L and T_H are related to their counterparts in the reference sample by two adjustable parameters: $\theta_D^{\text{sam}}(T_L) = r_1 \theta_D^{\text{ref}}(T_L)$, and

$\theta_D^{sam}(T_H) = r_2 \theta_D^{ref}(T_H)$. The parameter r_2 was determined from the requirement that C_{mag} should vanish at T_H , resulting in a C_{lat} that tends to C_{tot} at T_H . For the present case of $\text{Sr}_3\text{CuPtO}_6$ with $\text{Sr}_3\text{ZnPtO}_6$ as the reference sample, the single parameter correction factor (r)(which is valid in the low T region *i.e.*, $T \ll \Theta_D$ only) estimated from the difference in the mass of the atoms

is almost equal to 1³⁰. Therefore, the parameter r_1 was chosen as the smallest value for which C_{lat} does not cross C_{tot} over the whole T -range. The estimated values of the parameters are: $r_1 = 1.025$ and $r_2 = 1.050$ (with $T_L = 2$ K and $T_H = 300$ K). Figure 3 shows the corresponding lattice contribution of $\text{Sr}_3\text{CuPtO}_6$ that was obtained by including $\theta_D^{sam}(T)$ in the Debye formula.

-
- ¹ K. E. Stitzer, and H.-C. zur Loye, Current Opinion in Solid State and Material Science **5**, 535 (2001).
 - ² T. N. Nguyen, D. M. Giaquinta, and H.-C. zur Loye, Chem. Mater. **6**, 1642 (1994).
 - ³ J. Claridge, R. C. Layland, W. Hampton Henley, and H.-C. zur Loye, Chem. Mater. **11**, 1376 (1999).
 - ⁴ T. N. Nguyen, P. A. Lee, and H.-C. zur Loye, Science **271**, 489 (1996).
 - ⁵ J. L. Hodeau, H. Y. Tu, P. Bordet, T. Fournier, P. Strobel, and M. Marezio, Acta Cryst. B **48**, 1 (1992).
 - ⁶ W. E. Hatfield, J. Appl. Phys. **52**, 1985 (1981).
 - ⁷ S. H. Irons, T. D. Sangrey, K. M. Beauchamp, M. D. Smith and H. C. zur Loye, Phys. Rev. B **61**, 11594 (2000).
 - ⁸ A. Niazi, E. V. Sampathkumaran, P. L. Paulose, D. Eckert, A. Handstein, and K.-H. Müller Phys. Rev. B **65**, 064418 (2002).
 - ⁹ S. Rayaprol, Kausik Sengupta, and E. V. Sampathkumaran, Phys. Rev. B **67**, 180404(R) (2003).
 - ¹⁰ Kausik Sengupta, S. Rayaprol, Kartik K. Iyer, and E. V. Sampathkumaran, Phys. Rev. B **68** 012411 (2003).
 - ¹¹ V. Hardy, S. Lambert, M. R. Lees, and D. McK. Paul, Phys. Rev. B **68**, 014424 (2003).
 - ¹² J. C. Bonner and M. E. Fisher, Phys. Rev. **135**, A640 (1964).
 - ¹³ D. C. Johnston, R. K. Kremer, M. Troyer, X. Wang, A. Klümper, S. L. Bud'ko, A. F. Panchula, and P. C. Canfield, Phys. Rev. B **61**, 9558 (2000).
 - ¹⁴ A. Klümper, and D. C. Johnston, Phys. Rev. Lett. **84**, 4701 (2000).
 - ¹⁵ S. Eggert, I. Affleck, and M. Takahashi, Phys. Rev. Lett. **73**, 332 (1994).
 - ¹⁶ S. Lukyanov, Nucl. Phys. B **522**, 533 (1998).
 - ¹⁷ C. L.-Önnerud, M. Sigrist, and H.-C. zur Loye, J. Solid State Chemistry **127**, 25 (1996).
 - ¹⁸ M. Matsuda and K. Katsumata, Phys. Rev. B **53**, 12201 (1996).
 - ¹⁹ V. Kiryukhin, Y. J. Kim, K. J. Thomas, F. C. Chou, R. W. Erwin, Q. Huang, M. A. Kastner, and R. J. Birgeneau, Phys. Rev. B **63**, 144418 (2001).
 - ²⁰ Y. Liu, J. E. Drumheller, and R. D. Willett, Phys. Rev. B **52**, 15327 (1995).
 - ²¹ N. Motoyama, H. Eisaki and S. Uchida, Phys. Rev. Lett. **76**, 3212 (1996).
 - ²² In order to calculate S_{mag} , we have used our $C_{mag}(T)$ data in the temperature range 0.35 to 300 K and extrapolated down to 0 K.
 - ²³ T. Oguchi, Phys. Rev. **133**, A1098 (1964).
 - ²⁴ L. J. De Jongh and A. R. Miedema, Adv. Phys. **23**, 1 (1974).
 - ²⁵ H. J. Schulz, Phys. Rev. Lett. **77**, 2790 (1996).
 - ²⁶ M. E. Lines, and M. Eibschütz, Phys. Rev. B **11**, 4583 (1975).
 - ²⁷ E. Lieb, T. D. Schulz and D. C. Mattis, Ann. Phys. **16**, 407 (1961).
 - ²⁸ J. C. Bonner, and H. W. J. Blöte, Phys. Rev. B **25**, 6959 (1982).
 - ²⁹ R. L. Carlin, *Magnetochemistry* (Springer-Verlag, Berlin, 1986), p. 75.
 - ³⁰ M. Bouvier, P. Lethuillier, and D. Schmitt, Phys. Rev. B, **43**, 13137 (1991).